


Nitriding characteristics


An example of micro structure nitrided by PS process

● PS process


Daido Die & Mold Steel Solutions originally developed process featured by high scuffing and erosion resistance

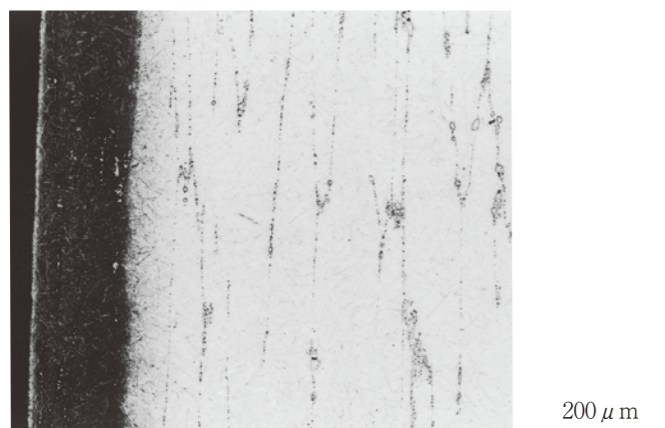

● Hardness distribution

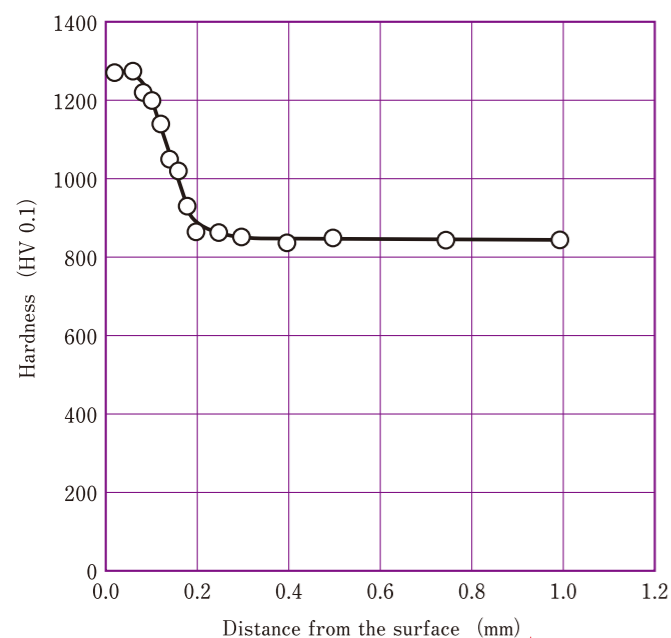

Drilling machinability

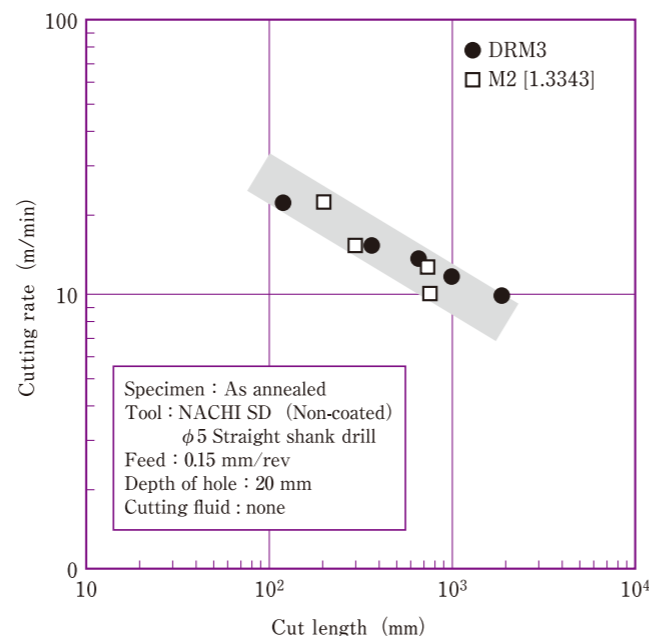

Physical properties

◆ Thermal expansion rate

Temp.	20~100°C	20~200°C	20~300°C	20~400°C	20~500°C	20~600°C
$\times 10^{-6}/K$	10.5	11.1	11.5	11.9	12.3	12.6

◆ Thermal conductivity

Temp.	25°C	100°C	200°C	300°C	400°C	500°C	600°C
W/m·K	20.2	22.6	24.8	25.5	26.0	26.4	27.6

*Accuracy of repeated measurements is about $\pm 10\%$.

◆ Specific heat

Temp.	25°C	100°C	200°C	300°C	400°C	500°C	600°C
J/kg·K	465	505	545	568	603	658	758

◆ Young's modulus / Rigidity modulus / Poisson's ratio (25°C)

Young's modulus	Rigidity modulus	Poisson's ratio
214GPa	82GPa	0.30

Quenching: 1140°C \times 1h, Oil cooling
Tempering: 560°C \times 1h - Air cooling, Twice
Hardness: 65HRC

Dream Series Daido's DRM3™

Cold Forging Die Steel

High hard and tough high speed tool steel with excellent hardenability

Features

Conventional grade MH88 has been improved to DRM3. High hardness and tough DRM3 with excellent hardenability is suitable for high precision cold working tools.

- ① Applicable with the maximum hardness 66HRC
- ② Fine carbides contribute higher toughness and fatigue strength than those of M2 [1.3343]
- ③ Greater hardenability results in high performance even in large dies and gas quenching in vacuum furnace.
- ④ Double melting realizes clean and homogeneous steel with less non-metallic inclusions

Applications

- Cold forging dies and punches
- Cold work roll, emboss roll
- Tools quenched by gas in vacuum furnace


Heat treatment

Re-forging Temperature	Heat treatment (°C)			Hardness	
	Annealing	Quenching	Tempering	Annealed	Quenched & Tempered
Requested to inquire	800~880 Slow cooling	1100~1140 OQ, GC, Salt bath	550~620 AC, \geq twice	\leq 235HBW	62~66HRC

OQ : Oil quenching, GC : Gas quenching in vacuum furnace, AC : Air cooling

Microstructure (As annealed)

- Finely distributed coarse carbides

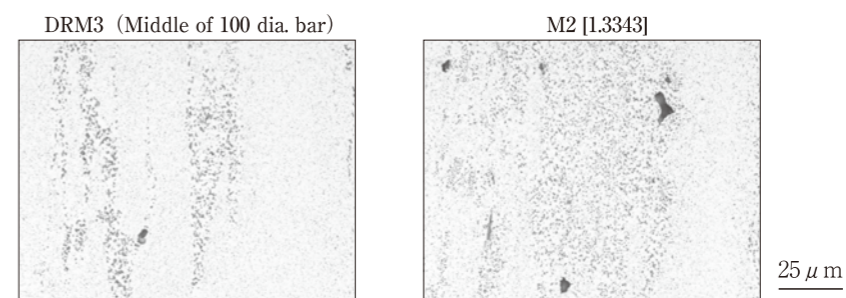

(Cr₂O₃ Electrically etching)



Tokyo Head Office
(Tool Steel Div. Tool Steel Marketing & Sales Dept. Overseas Sect.)

Daido Shinagawa Building, 6-35, 1-Chome, Konan, Minato-ku, Tokyo, Japan
Phone: +81-3-5495-1270 Fax: +81-3-5495-6739

Bangkok Office

Unit2-1, 22nd Fl., Silom Complex Bldg., 191, Silom Road, Silom, Bangkok, Bangkok 10500, Thailand
Phone: +66-2-231-3214 Fax: +66-2-231-3216

Daido Steel Group Europe GmbH

Insterburger Strasse 16, 60487 Frankfurt am Main, Germany
Phone: +49-69-29802867-0 Fax: +49-69-29802867-40

Daido Steel (America) Inc.

1051 Perimeter Drive, Suite 1175, Schaumburg, Illinois 60173, U.S.A.
Phone: +1-847-517-7950 Fax: +1-847-517-7951

Daido Steel (Shanghai) Co., Ltd

Room 1402, Ruijin Building, 205 Mao Ming Nan Road, Shanghai, 200020, China
Phone: +86-21-5466-2020 Fax: +86-21-5466-0279

Daido Steel (Shanghai) Co., Ltd
Guangzhou Subsidiary Company

Room 2601, No.8, Linhezhong Road, Tianhe District, Guangzhou, 510610, China
Phone: +86-20-3877-1632 Fax: +86-20-8550-1126

www.daido.co.jp

DRM is a Registered trademark or Trademark of Daido Steel Co., Ltd.

■ Document Disclaimer

The product characteristics included in this brochure are the representative values based on the result of our measurements, and do not guarantee the performance in use of the products.

Please inquire the latest information to our department in charge as the information of this brochure is updated without previous notice as needed.


Copyright © 2005 Daido Steel Co., Ltd. All rights reserved.

No.SC0409a 23.03.0.0 (ZZZ)




Properties

Tempered Hardness

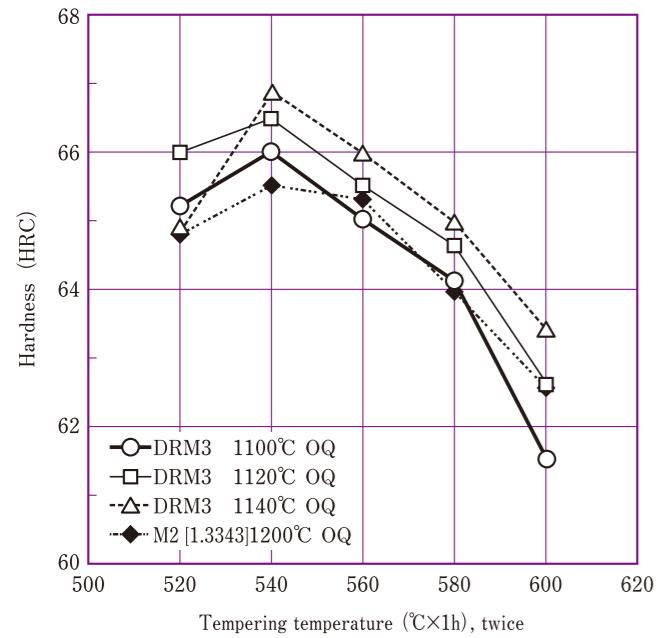


- Specimen : 15mm square
- Hardening : Oil quenching
- Tempering : Air cooling

Toughness

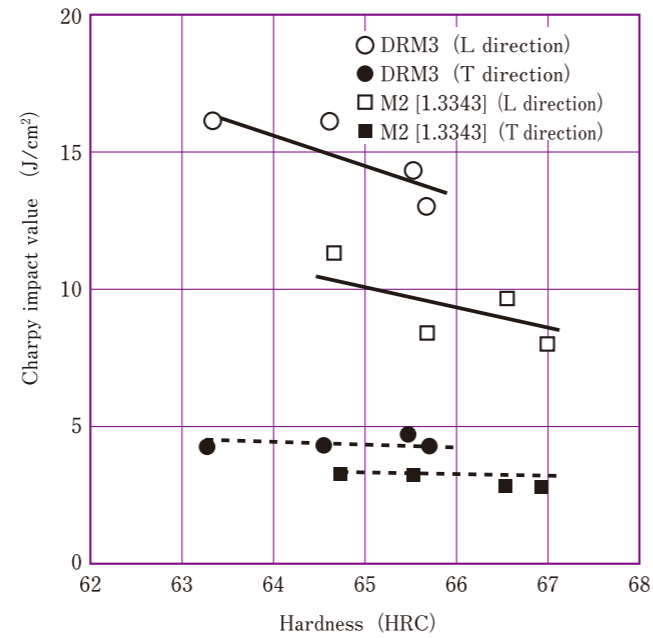


- Sampling : 100mm dia. Bar center
- Specimen : 10R notched
- Heat treatment : DRM3 H : 1140°C OQ
T : 540~600°C AC, twice
- Heat treatment : M2 [1.3343] H : 1210°C OQ
T : 540~600°C AC, twice

Heat checking resistance

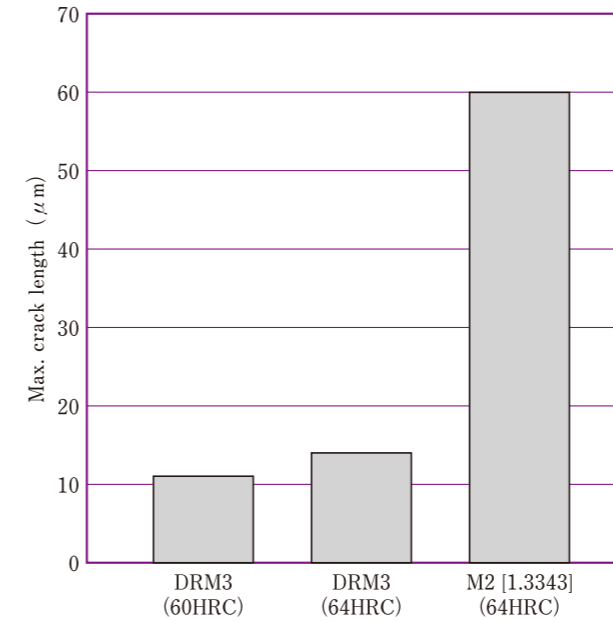


- Specimen : 15 mm dia. 10 mm thick
- Heat treatment : DRM3 H : 1120°C OQ
T : 560~620°C AC, twice
- Heat treatment : M2 [1.3343] H : 1200°C OQ
T : 560°C AC, twice
- Test method : Induction heating 20 → 600°C (1000 times)

Fatigue strength

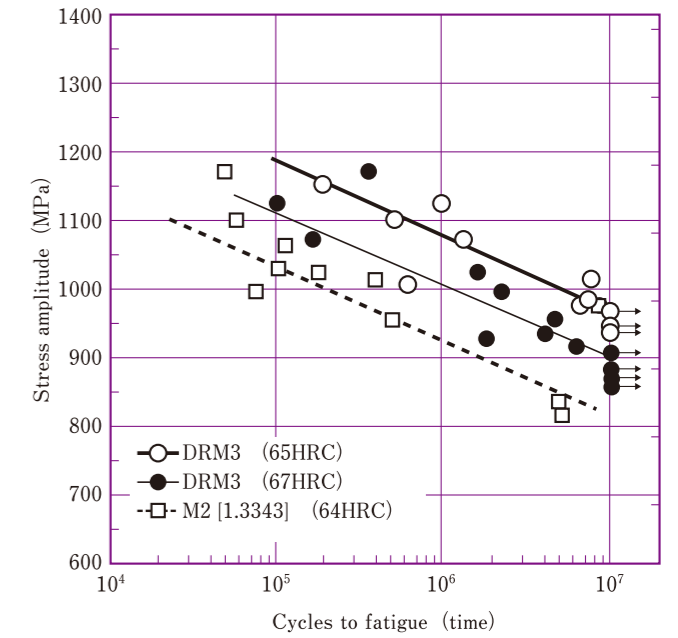

- Heat treatment : DRM3 (65HRC) H : 1100°C OQ
T : 560°C AC, twice
- Heat treatment : DRM3 (67HRC) H : 1140°C OQ
T : 550°C AC, twice
- Heat treatment : M2 [1.3343] H : 1200°C OQ
T : 560°C AC, twice
- Test method : Rotating bending fatigue test (20°C)


Hot hardness

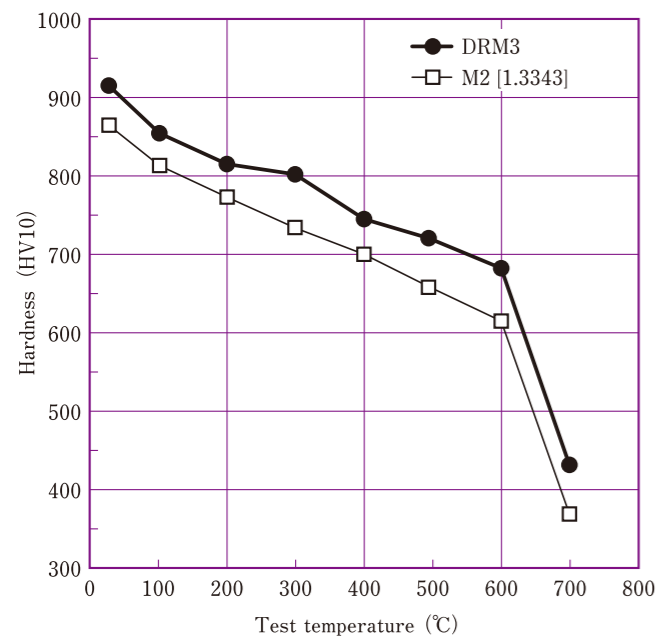


- Heat treatment : DRM3 H : 1140°C OQ
T : 560°C AC, twice
- Heat treatment : M2 [1.3343] H : 1200°C OQ
T : 580°C AC, twice

Hardenability


Quenching cooling rate VS Bending strength Hardness

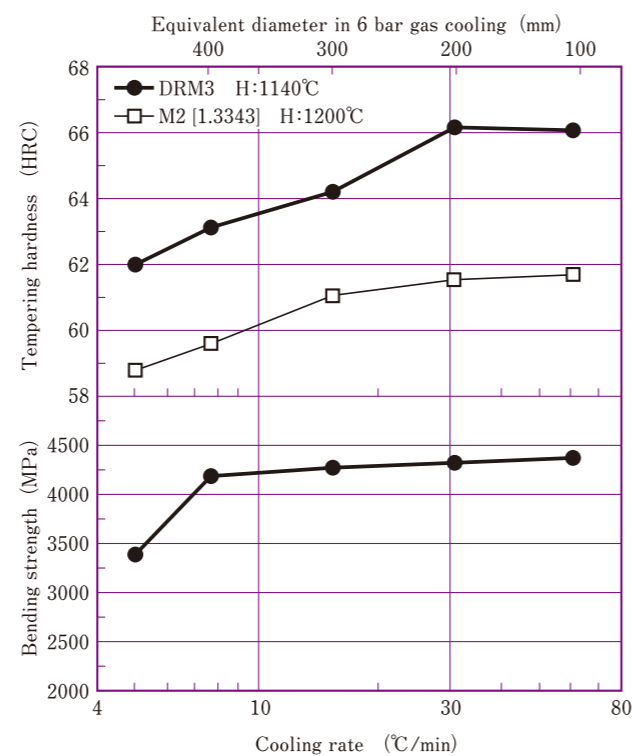

CCT diagram

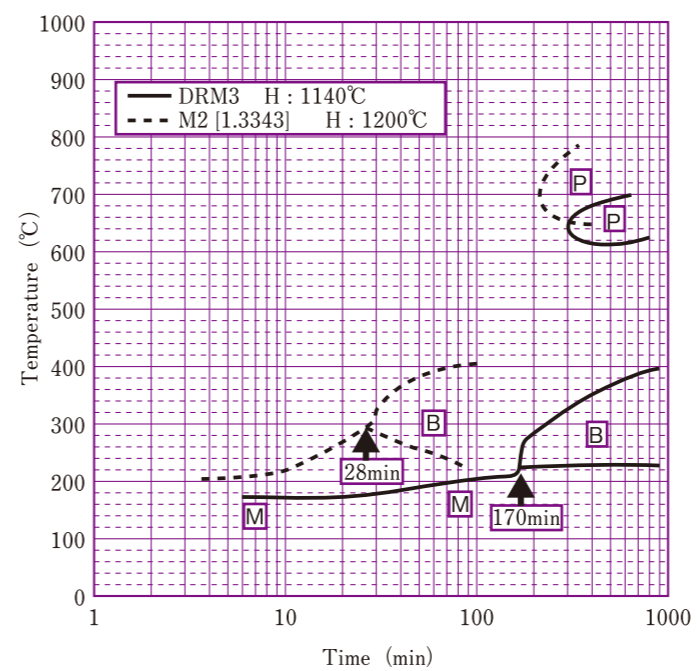

Dimensional change

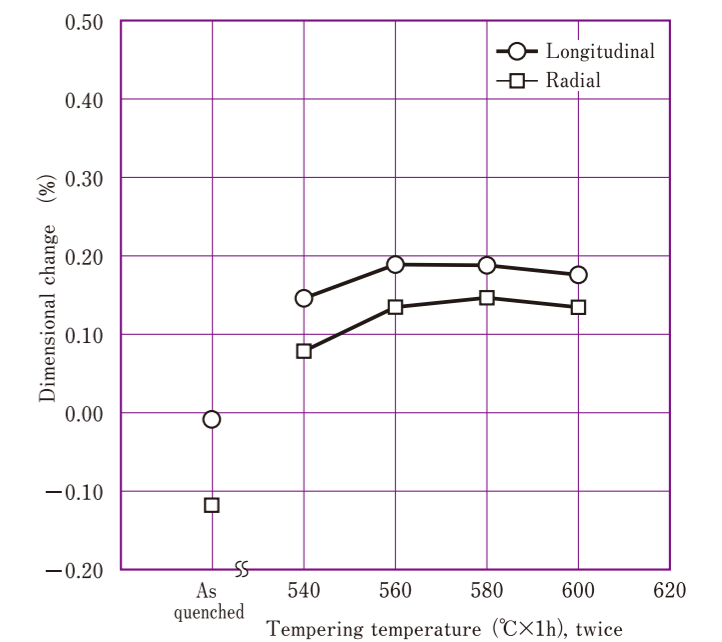

- Specimen : 100mm dia. x 60 mm
- Hardening : 1140°C salt bath quenching